


Synthesis and Catalytic Properties of Metal Clusters Encapsulated within Small-Pore (SOD, GIS, ANA) Zeolites

Sarika Goel, Zhijie Wu,[†] Stacey I. Zones,[‡] and Enrique Iglesia*

Department of Chemical and Biomolecular Engineering, University of California at Berkeley, Berkeley, California 94720, United States

Supporting Information

ABSTRACT: The synthesis protocols for encapsulation of metal clusters reported here expand the diversity in catalytic chemistries made possible by the ability of microporous solids to select reactants, transition states, and products on the basis of their molecular size. We report a synthesis strategy for the encapsulation of noble metals and their oxides within SOD (Sodalite, 0.28 nm × 0.28 nm), GIS (Gismondine, 0.45 nm × 0.31 nm), and ANA (Analcime, 0.42 nm × 0.16 nm) zeolites. Encapsulation was achieved via direct hydrothermal synthesis for SOD and GIS using metal precursors stabilized by ammonia or organic amine ligands, which prevent their decomposition or precipitation as colloidal hydroxides at the conditions of hydrothermal synthesis (<380 K) and favor interactions between metal precursors and incipient aluminosilicate nuclei during self-assembly of microporous frameworks. The synthesis of ANA requires higher crystallization temperatures (~415 K) and high pH (>12), thereby causing precipitation of even ligand-stabilized metal precursors as hydroxides. As a result, encapsulation was achieved by the recrystallization of metal clusters containing GIS into ANA, which retained these metal clusters within voids throughout the GIS–ANA transformation.

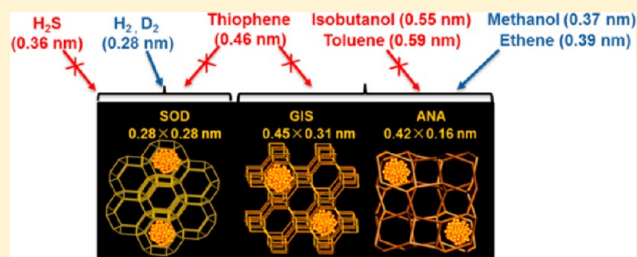

INTRODUCTION

Encapsulation of metal and oxide clusters within zeolites^{1–5} can protect such clusters against sintering and also prevent their contact with toxic impurities, while concurrently allowing active sites to select reactants and transition states on the basis of molecular size.^{6–10} The confinement of such clusters within small-pore zeolites (<0.45 nm apertures) cannot be achieved via post-synthesis exchange from aqueous or vapor media, because the size of cationic or anionic precursors, with their charge-balancing double layer, and of gaseous complexes prevents their diffusion through the apertures in these microporous aluminosilicates. In these materials, encapsulation requires that precursors be placed and retained within microporous frameworks during hydrothermal syntheses and subsequent thermal treatment.^{9,11} The high pH (>12) conditions required for hydrothermal crystallization of zeolites typically cause the precipitation of such precursors as colloidal metal hydroxides larger than the zeolite voids,¹² thus preventing their encapsulation. Organic amines and NH₃ ligands can stabilize metal cations and prevent premature precipitation; they can also act as coordinating agents to encourage the sequestering of precursors during the incipient formation of aluminosilicate frameworks.¹³

Hydrothermal synthesis of zeolites proceeds via three steps: induction, nucleation, and crystallization.¹⁴ The framework building units are denoted as the “host” and the external component as the “guest”. Zeolite nucleation and crystallization hinges on a balance of guest–host assembly with the guest

stabilizing the surrounding zeolite framework.¹⁵ The ligand-stabilized metal cationic complexes used here are hydrophilic and are very effective in templating Al-rich zeolites (Sodalite (SOD), Analcime (ANA), and Gismondine (GIS))¹⁶ during hydrothermal synthesis, in contrast with Si-rich zeolites, which require hydrophobic organo-cations as stabilizing guests and structure-directing agents.¹⁷

We present here synthetic protocols for the encapsulation of active metals within zeolites with small voids (SOD, GIS, and ANA, Figure 1) and show that such zeolite structures can protect Pt, Pd, Ru, and Rh clusters against sintering and from contact with larger molecules that block active surfaces. These data also provide chemical and structural evidence for

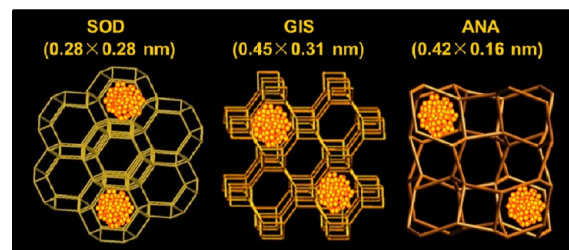


Figure 1. Pictorial representation of metal clusters encapsulated within zeolites and zeolite aperture sizes.

Received: July 26, 2012

Published: September 27, 2012

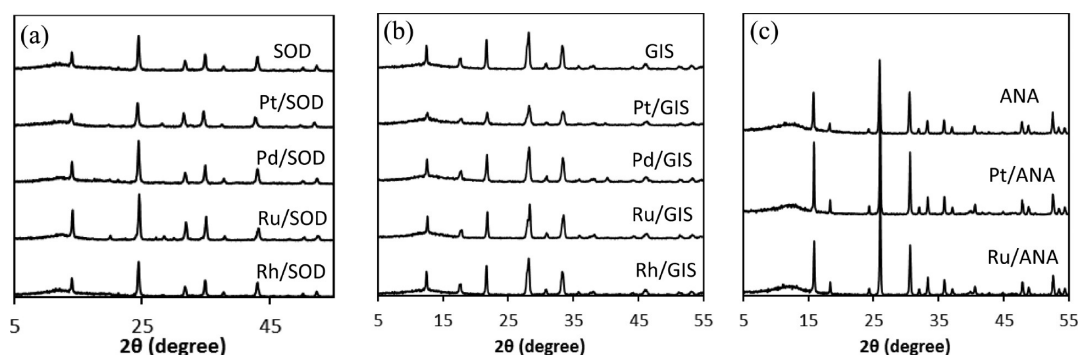


Figure 2. X-ray diffraction patterns of (a) M/SOD, (b) M/GIS, and (c) M/ANA samples (M = Pt, Pd, Ru, Rh).

confinement and for the consequences of encapsulation on catalytic rates and selectivity. Precursor stabilization during synthesis proved infeasible for ANA because of the high temperatures required for its crystallization (~ 415 K). GIS structures already containing reduced metal clusters were instead converted into ANA via local recrystallization processes that retained metal clusters within ANA crystals.

Encapsulation and phase purity were established using X-ray diffraction, transmission electron microscopy, and titration methods. Oxidative dehydrogenation (ODH) of methanol (kinetic diameter 0.37 nm) and isobutanol (kinetic diameter 0.55 nm), hydrogenation of ethene (kinetic diameter 0.39 nm) and toluene (kinetic diameter 0.59 nm), and ethene hydrogenation in the presence and absence of thiophene (kinetic diameter 0.46 nm) were used to confirm encapsulation and to establish the ability of metal-containing GIS and ANA catalysts to select reactants on the basis of size and to protect active sites from large organosulfur poisons. $\text{H}_2\text{-D}_2$ (kinetic diameter 0.28 nm) isotopic exchange in the presence and absence of H_2S (kinetic diameter 0.36 nm) was used to probe the ability of metal-containing SOD to activate dihydrogen without interference by H_2S .

RESULTS AND DISCUSSION

The direct encapsulation of metal precursors during hydrothermal synthesis requires interactions between metal precursors and incipient aluminosilicate frameworks, which are favored by cationic metal complexes because of the anionic nature of aluminosilicate building blocks.¹¹ Encapsulation requires the self-assembly of these building blocks around solvated cations.¹² At the high pH (>12) of hydrothermal syntheses, these cations precipitate prematurely as colloidal hydroxides (Supporting Information Table S1, precipitation time for metal precursors in alkaline solution) that cannot be contained within the voids in incipient aluminosilicate frameworks, thus preventing encapsulation. Ammonia and ethylene diamine ligands stabilize cationic precursors and prevent their precipitation, even at higher pH (up to ~ 13) and temperatures above ambient (up to ~ 390 K). Additionally, these ligands can act as tethers between cationic complexes and the emerging aluminosilicate moieties that ultimately assemble into zeolite frameworks, thus favoring the inclusion of metal precursors within SOD and GIS zeolite voids as they form. ANA requires higher temperature (~ 415 K) for crystallization, which leads to rapid formation of metal hydroxides even when metal precursors are stabilized by ligands (Figure S1, Supporting Information). The synthesis of ANA involves the initial formation of GIS, which then converts to ANA.¹⁸ These

observations led us to attempt the recrystallization of metal encapsulated within GIS (M/GIS) into metal encapsulated within ANA (M/ANA) while retaining metal clusters within crystallites.

Structural Evidence for Zeolite Phase and for Confinement and Surface Cleanliness of Metal and Oxide Clusters. X-ray diffraction (XRD) patterns for metal-containing zeolites (M/SOD, M/GIS, and M/ANA) (Figure 2) showed lines corresponding to crystalline forms of the intended zeolite structures, indicating that ligated precursors did not interfere with hydrothermal crystallization processes. Transmission electron micrographs (TEM) for M/GIS and high-angle annular dark-field scanning transmission electron micrographs (HAADF STEM) (Figure 3) after reduction of precursors and passivation of metal clusters showed that they were present as small clusters uniform in size and distributed throughout zeolite crystallites. The metal clusters in SOD were not visible by TEM, but HAADF STEM images show the presence of small clusters (1.0–1.5 nm, Figure 3) in Pt/SOD.

H_2 uptakes gave metal dispersions of 0.63–0.70 for Pt, Pd, Ru, and Rh clusters in GIS, 0.50–0.61 for Pt and Ru in ANA, and 0.22–0.39 for Pt, Pd, Ru, and Rh in SOD (Table 1) after thermal treatment at 573 K. The dispersion values obtained from H_2 -chemisorption in SOD samples are small compared to the values expected on the basis of electron microscopy due to the limited access of even hydrogen to active sites tightly contained within small aperture SOD cages. The agreement between surface-averaged mean diameters from electron micrographs in M/GIS (M = Pt, Pd, Ru, and Rh) and Pt/ANA and those determined from H_2 chemisorption uptakes (assuming spherical clusters; Figure 3) indicates that all clusters detectable by microscopy exhibit clean surfaces accessible to these titrants and that the ligands present during hydrothermal synthesis are removed by the thermal treatments used. We conclude from these data that metal cluster surfaces are available for catalytic reactions of any reactants that can diffuse through the microporous frameworks in GIS and ANA zeolites at rates commensurate with those of the surface-catalyzed chemical reactions.

Catalytic Evidence for Encapsulation: Oxidative Dehydrogenation of Methanol and Isobutanol and Hydrogenation of Ethene and Toluene on GIS- and ANA-Supported Catalysts. The molecular dimensions of GIS and ANA apertures allow them to sieve reactants and products on the basis of size, while the intervening intracrystal voids can stabilize specific transition states that maximize their van der Waals contacts with the framework. Oxidative dehydrogenation (ODH) rates of methanol¹⁹ and isobutanol

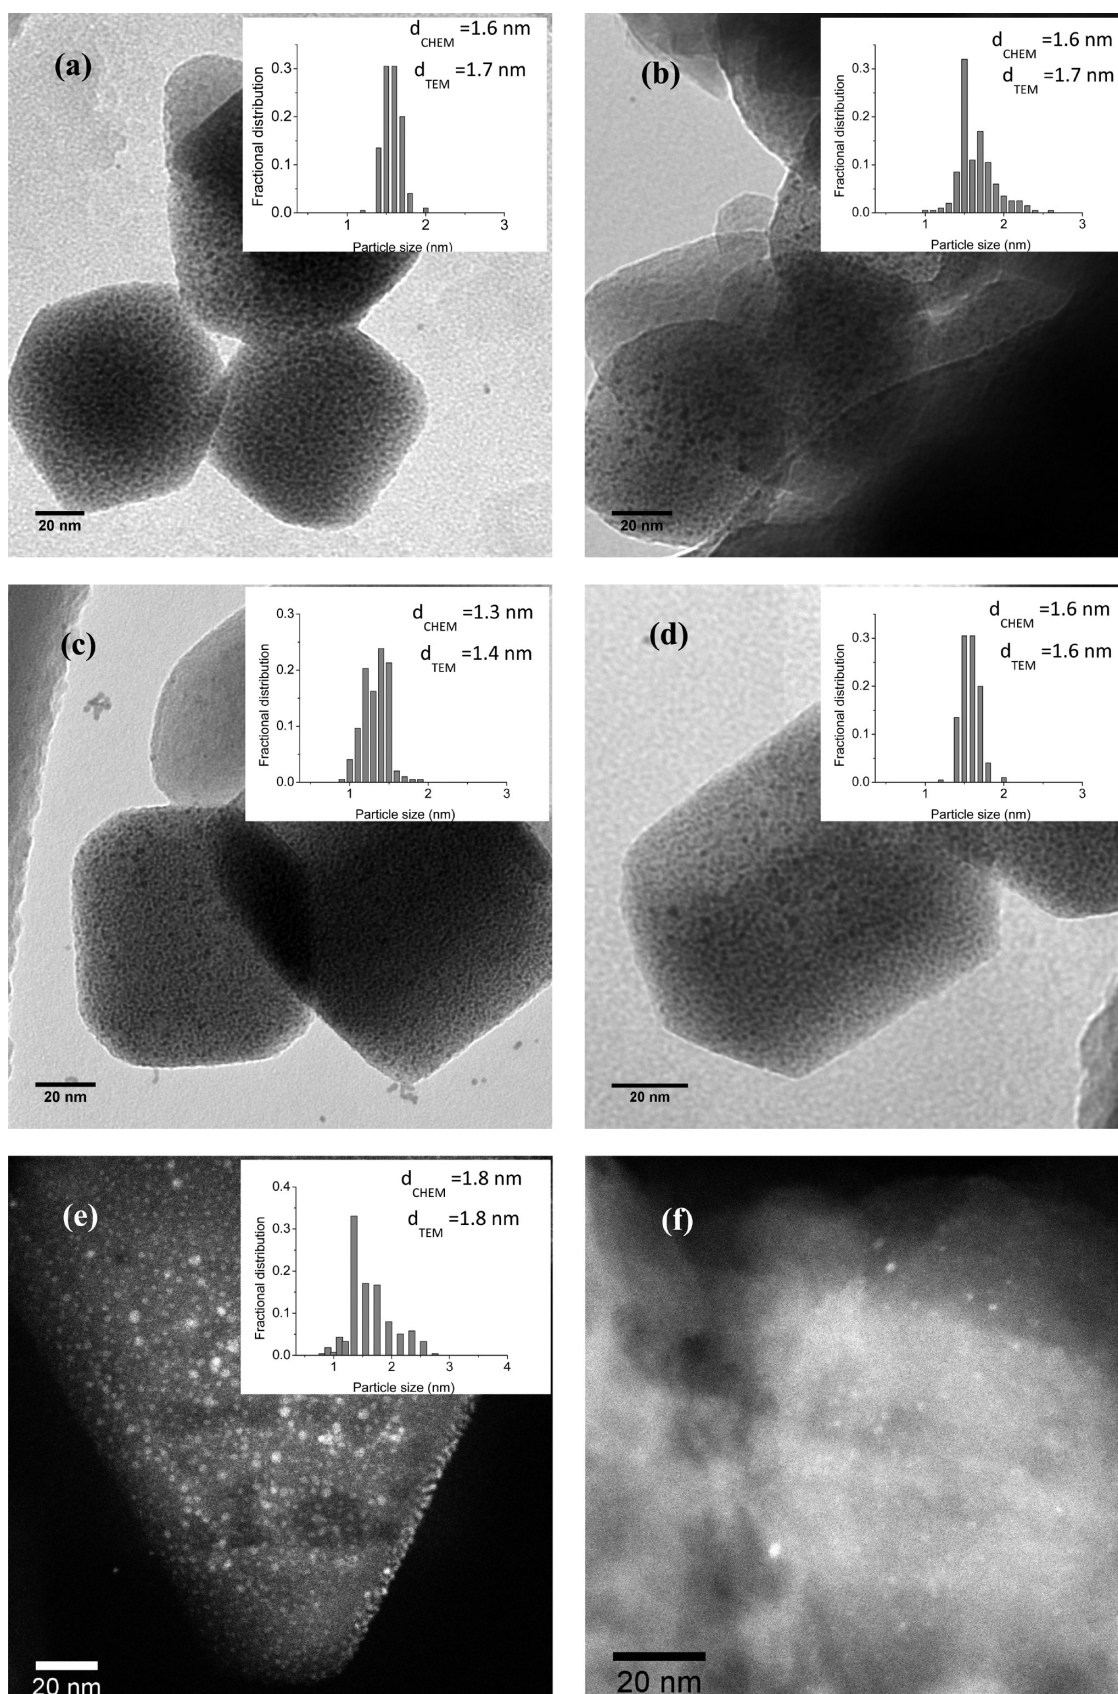


Figure 3. Metal clusters size distributions and TEM images of (a) Pt/GIS, (b) Pd/GIS, (c) Ru/GIS, (d) Rh/GIS, and HAADF STEM images of (e) Pt/ANA and (f) Pt/SOD samples. Surface-weighted metal cluster size diameters, d_{TEM} , were calculated using $d_{\text{TEM}} = \frac{\sum n_i d_i^3}{\sum n_i d_i^2}$. Metal clusters size distribution is not included for Pt/SOD because it was difficult to locate enough platinum clusters to be able to get a statistical value for average cluster size.

Table 1. Metal Precursors, Loadings, and Dispersions of Metal Clusters (Pt, Pd, Ru, Rh) Dispersed in SiO₂, SOD, GIS, and ANA Samples

sample	precursor used	metal loading ^a (wt %)	metal dispersion ^b (fraction)
Pt/SiO ₂	[Pt(NH ₃) ₄](NO ₃) ₂	0.79	0.61
Pd/SiO ₂	[Pd(NH ₃) ₄](NO ₃) ₂	0.55	0.69
Ru/SiO ₂	[Ru(NH ₃) ₆]Cl ₃	0.50	0.50
Rh/SiO ₂	[Rh(NH ₃) ₅]Cl ₂	1.10	0.60
Pt/SOD	[Pt(NH ₃) ₄](NO ₃) ₂	0.10	0.38
Pd/SOD	[Pd(NH ₂ CH ₂ CH ₂ NH ₂) ₂]Cl ₂	0.10	0.23
Ru/SOD	[Ru(NH ₃) ₆]Cl ₃	0.034	0.22
Rh/SOD	[Rh(NH ₂ CH ₂ CH ₂ NH ₂) ₃]Cl ₃ ·3H ₂ O	0.045	0.39
Pt/GIS	[Pt(NH ₃) ₄](NO ₃) ₂	0.86	0.70
Pd/GIS	[Pd(NH ₂ CH ₂ CH ₂ NH ₂) ₂]Cl ₂	0.85	0.68
Ru/GIS	[Ru(NH ₃) ₆]Cl ₃	0.40	0.63
Rh/GIS	[Rh(NH ₂ CH ₂ CH ₂ NH ₂) ₃]Cl ₃ ·3H ₂ O	0.24	0.67
Pt/ANA	[Pt(NH ₃) ₄](NO ₃) ₂	1.00	0.61
Ru/ANA	[Ru(NH ₃) ₆]Cl ₃	0.50	0.50

^aAnalyzed by inductively coupled plasma optical emission spectroscopy. ^bMetal dispersions estimated from H₂ chemisorptions.

Table 2. Catalytic Properties of Metal Clusters (Pt, Pd, Ru, Rh) Dispersed in GIS, ANA, and SiO₂ in Oxidative Dehydrogenation of Alkanols^a

sample	r_{methanol}^b (mol·(mol _{surf-metal}) ⁻¹ ·s ⁻¹)	$r_{\text{isobutanol}}^b$ (mol·(mol _{surf-metal}) ⁻¹ ·s ⁻¹)	$\chi_{\text{ODH},j}^c$ j = zeolite, SiO ₂	ϕ^d
Pt/GIS	3.56	0.0191	186.4	
Pt/SiO ₂	7.02	1.45	4.8	38.5
Pd/GIS	0.20	0.0104	19.4	
Pd/SiO ₂	0.51	0.23	2.2	8.8
Ru/GIS	0.13	0.0017	76.4	
Ru/SiO ₂	0.05	0.04	1.2	70.0
Rh/GIS	0.17	0.0016	107.6	
Rh/SiO ₂	0.19	0.15	1.3	82.7
Pt/ANA	0.33	0.0021	160.9	
Pt/SiO ₂	7.02	1.45	4.8	33.2
Ru/ANA	0.02	0.0003	66.6	
Ru/SiO ₂	0.05	0.04	1.2	55.5

^aAlkanol oxidative dehydrogenation reactions were carried out with 4 kPa alkanols and 9 kPa O₂ at 393 K. ^bReaction turnover rate is defined as mole of reactant converted per mol of surface metal atoms per second. ^c $\chi_{\text{ODH},j} = r_{\text{methanol}}/r_{\text{isobutanol}}$ j = zeolite, SiO₂. ^d $\phi = \chi_{\text{ODH},\text{zeolite}}/\chi_{\text{ODH},\text{SiO}_2}$.

Table 3. Catalytic Properties of Pt Dispersed in GIS, ANA, and SiO₂ in Hydrogenation of Ethene^a and Toluene^b

sample	r_{ethene}^c (mol·(mol _{surf-metal}) ⁻¹ ·s ⁻¹)	r_{toluene}^c (mol·(mol _{surf-metal}) ⁻¹ ·s ⁻¹)	$\chi_{\text{HYD},j}^d$ j = zeolite, SiO ₂	ϕ^e
Pt/GIS	2.90	0.012	241.6	
Pt/SiO ₂	5.26	1.38	3.8	63.4
Pt/ANA	2.00	0.011	181.8	
Pt/SiO ₂	5.26	1.38	3.8	47.7

^aEthene hydrogenation reactions were carried out with 0.95 kPa ethene and 5 kPa H₂ at 308 K. ^bToluene hydrogenation reactions were carried out with 0.35 kPa toluene, 99.65 kPa H₂ at 473 K. ^cReaction turnover rate is defined as mole of reactant converted per mole of surface metal atoms per second. ^d $\chi_{\text{HYD},j} = r_{\text{ethene}}/r_{\text{toluene}}$ j = zeolite, SiO₂. ^e $\phi = \chi_{\text{HYD},\text{zeolite}}/\chi_{\text{HYD},\text{SiO}_2}$.

(0.37 and 0.55 nm respective kinetic diameters) and hydrogenation of ethene and toluene (0.39 and 0.59 nm respective kinetic diameters) were used to confirm the predominant presence of Pt, Pd, Ru, and Rh clusters within GIS (0.45 nm × 0.31 nm aperture) and of Pt and Ru clusters within ANA (0.42 nm × 0.16 nm aperture). Methanol and ethene, but not isobutanol and toluene, can access sites encapsulated within GIS or ANA zeolite crystals via diffusion through their interconnected voids and apertures.

The selectivity of encapsulation processes during hydrothermal synthesis was assessed by first measuring the ratio of ODH and hydrogenation rates for the small and large reactants

on unconstrained clusters dispersed on SiO₂ ($\chi_{\text{ODH},\text{SiO}_2} = r_{\text{methanol}}/r_{\text{isobutanol}}$, $\chi_{\text{HYD},\text{SiO}_2} = r_{\text{ethene}}/r_{\text{toluene}}$) to determine the relative reactivity of these two molecules on unconstrained systems; similar data for the same metal in zeolite samples ($\chi_{i,\text{zeolite}}$, i = ODH, HYD) allow the ratio of these relative reactivities to be expressed as an encapsulation selectivity parameter ($\phi = \chi_{i,\text{zeolite}}/\chi_{i,\text{SiO}_2}$, i = ODH, HYD) for each reaction and reactant pair. This ratio represents a direct measure of the diffusional constraints imposed on larger reactants by the presence of metal clusters within zeolite structures; it is therefore a rigorous indicator of the extent to

which the active surfaces are contained within the microporous networks. This encapsulation selectivity parameter would approach unity for clusters with unimpeded access to reactants, such as those at external zeolite surfaces. Values of ϕ provide the functional definition of the effectiveness of synthetic protocols, as well as the mechanistic and practical manifestation of reactant shape selectivity; values larger than ~ 5 are taken here as evidence of successful encapsulation.

M/GIS and M/ANA samples gave much larger $\chi_{\text{ODH,zeolite}}$ and $\chi_{\text{H2D,zeolite}}$ values than the respective metals dispersed on SiO_2 (Tables 2 and 3) and high encapsulation selectivities ($\phi = 8\text{--}83$, Figure 4) for both ODH and hydrogenation reactions,

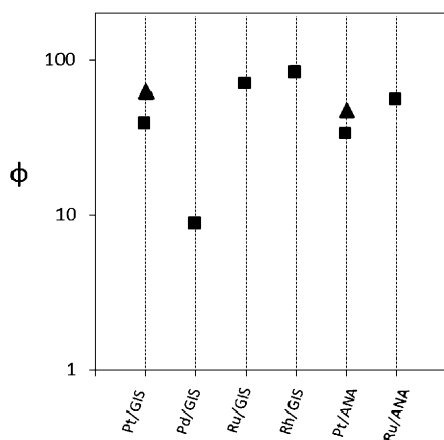


Figure 4. Encapsulation selectivity parameter (ϕ), reflecting the shape selectivity for various M/GIS and M/ANA samples (M = Pt, Pd, Ru, Rh) in alkanol oxidative dehydrogenation (ODH) (■) and ethene and toluene hydrogenation (▲). ϕ values larger than unity indicate the preferential containment of clusters within zeolite micropores that can sieve reactants on the basis of size.

indicating that active sites on these zeolites indeed reside predominantly within locations accessible only to the smaller methanol and ethene reactants. Methanol ODH and ethene hydrogenation turnover rates (per exposed metal atom determined from chemisorption uptakes) were smaller on metals dispersed on GIS and ANA than on SiO_2 , indicating that even for small ethene and methanol molecules access to active surface is restricted by diffusion through the zeolite aperture or by limited access to the active clusters tightly contained within zeolite cages.

Catalytic Evidence for the Protection of Active Sites from Large Sulfur Poisons: Hydrogenation of Ethene in the Presence and Absence of Thiophene in GIS- and ANA-Supported Catalysts. The diffusional constraints that restrict access to active sites by larger reactants also serve to prevent contact between encapsulated metal clusters and larger organosulfur poisons, such as thiophene, which titrate surface atoms and render them unreactive. These expectations were confirmed by measuring ethene (0.39 nm kinetic diameter) hydrogenation rates on Pt/GIS and Pt/ANA and on the respective metals dispersed on SiO_2 in the presence or absence of thiophene (0.46 nm kinetic diameter; 0.4 kPa) (Figure 5), an organosulfur titrant that cannot readily diffuse through the small apertures in GIS and ANA.

The addition of thiophene (0.4 kPa) to the reactants decreased ethene hydrogenation rates by a factor of 13 in Pt/GIS, 7 in Pt/ANA, and 530 in Pt/ SiO_2 . After thiophene addition was stopped, ethene hydrogenation rates recovered to

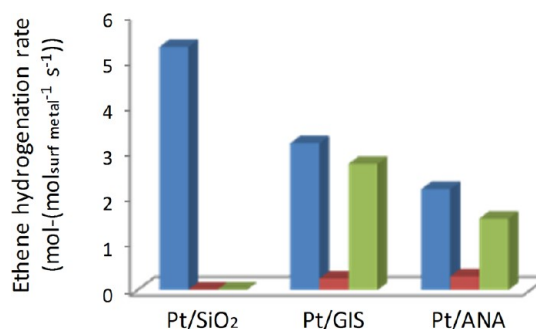


Figure 5. Ethene hydrogenation rate in Pt/ SiO_2 , Pt/GIS, and Pt/ANA samples without thiophene (blue), with 0.4 kPa thiophene added for 1 h (red), and after stopping thiophene injection (green). Ethene hydrogenation reaction was carried out with 0.95 kPa ethene, 5 kPa H_2 , and 0 kPa/0.4 kPa thiophene at 315 K. Reaction turnover rate is defined as ethene hydrogenation rate per mol of surface metal atoms per second.

0.85 of initial rate in Pt/GIS and 0.70 in Pt/ANA (Figure 5). In sharp contrast, metal clusters dispersed on SiO_2 did not show any detectable increase in hydrogenation rates after removal of thiophene from ethene- H_2 feed. The lower rates observed on Pt/ANA and Pt/GIS after thiophene addition appear to reflect the combined effects of titration of external clusters and diffusional constraints on ethene reactants imposed by thiophene physisorbed on external zeolite surfaces and blocking the zeolite aperture; the latter effects are reversible and disappear upon removal of thiophene.

The essential retention of ethene hydrogenation rates for metal clusters on GIS and ANA zeolites after stopping thiophene confirms that 0.70–0.85 fraction of the active metal cluster surfaces resides within GIS and ANA structures, where such active sites cannot contact the organosulfur compound.

Evidence of Encapsulation and Protection of Active Sites from Toxic Sulfur Compounds: $\text{H}_2\text{--D}_2$ Exchange Rates on SOD-Supported Catalysts. The smaller apertures in SOD (0.28 nm) allow the diffusion of H_2 (0.28 nm kinetic diameter) and D_2 (0.28 nm kinetic diameter), but few other molecules.²⁰ The protection of active sites from H_2S (0.36 nm kinetic diameter) was demonstrated by measuring $\text{H}_2\text{--D}_2$ exchange rates at 373 K in the absence and presence of H_2S (1 kPa) on Pt, Pd, Ru, and Rh clusters dispersed on SOD and the same metal clusters dispersed on SiO_2 .

The addition of H_2S to $\text{H}_2\text{--D}_2$ decreased $\text{H}_2\text{--D}_2$ exchange rates by a factor of 2.7–9.9 on SiO_2 -supported metals, as expected from the titration of exposed surface atoms by sulfur moieties derived from H_2S . In contrast, isotopic exchange rates decreased by much smaller factors (1.3–1.5) on M/SOD samples when H_2S (1 kPa) was present in $\text{H}_2\text{--D}_2$ reactants (Figure 6). Residual $\text{H}_2\text{--D}_2$ exchange rates on SiO_2 -supported clusters in the presence of H_2S (Figure 6) reflect exchange rates on S-containing surfaces, including exchange between H-atoms from H_2S and D-atoms in D_2 . H_2S inhibition of exchange rates in M/SOD reflects the combined effects of irreversible titration of external clusters by chemisorbed sulfur species and reversible H_2S physisorption at external SOD surfaces, which interferes with the diffusion of dihydrogen isotopes. The latter effect is reversible upon removal of H_2S from the $\text{H}_2\text{--D}_2$ reactants and leads to the partial recovery of exchange rates (Figure 6). The residual rates after H_2S removal rigorously reflect the rates on encapsulated surfaces on M/SOD samples never exposed to

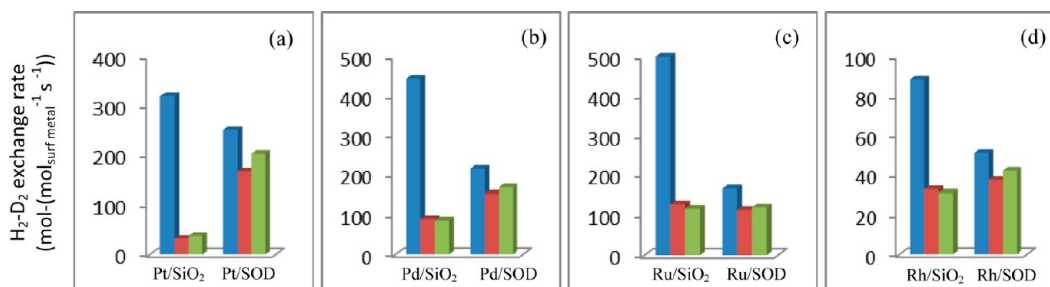


Figure 6. H₂-D₂ exchange rate in (a) Pt, (b) Pd, (c) Ru, and (d) Rh clusters dispersed on SiO₂ and SOD without H₂S (blue), with 1.0 kPa H₂S added for 1 h (red), and after stopping H₂S injection (green). H₂-D₂ exchange reactions were carried out with 50.05 kPa H₂, 49.95 kPa D₂, and 0 kPa/1 kPa H₂S at 373 K. Reaction turnover rate is defined as H₂-D₂ exchange rate per mol of surface metal atoms per second.

H₂S. H₂S removal from H₂-D₂ did not lead to any changes in exchange rates on unprotected clusters dispersed on SiO₂, because inhibition reflects only the titration of active metal surfaces without additional contributions from diffusional effects.

The exchange rates on M/SOD were corrected by rates measured on M/SiO₂ in the presence of H₂S to obtain the rate coming solely from H₂-D₂ exchange on metal clusters encapsulated within SOD framework. These calculations show that a large fraction of the active surfaces (0.64–0.79 fraction) are protected from H₂S in M/SOD samples, apparently because such surfaces reside within SOD crystals that are inaccessible to H₂S. These data show that encapsulated clusters within SOD can be effectively protected against all sulfur poisons, while concurrently demonstrating the high encapsulation selectivity achieved.

Practical Implications. Metal clusters encapsulated within ANA and GIS provide practical catalysts for the selective hydrogenation–dehydrogenation of linear hydrocarbons and oxygenates over branched or cyclic analogues as evidenced from selective oxidative dehydrogenation of methanol and isobutanol and selective hydrogenation of ethene and toluene (Figure 4). These catalysts can also effectively prevent inhibition of these reactions by larger and more strongly bound species, such as arenes and organosulfur compounds, as evidenced by the protection of active sites from thiophene poisons in ethene hydrogenation (Figure 5). The SOD-encapsulated clusters can potentially extract H₂ via dissociative adsorption from streams containing H₂S at ambient temperatures and subsequent desorption during temperature cycling. These materials reversibly chemisorb H₂ (Table 1) and retain their ability to do so in the presence of H₂S during H₂-D₂ exchange reactions (Figure 6).

CONCLUSION

Encapsulation of noble metals (Pt, Pd, Ru, and Rh) was achieved within small-pore zeolites (SOD and GIS) via direct hydrothermal synthesis using ligands that prevent precipitation as colloidal hydroxides at the high pH required for zeolite crystallization. ANA-encapsulated clusters were prepared by post-synthesis recrystallization of their metal-containing GIS analogues, because the high temperature required for direct ANA synthesis decomposed even ligand-protected metal precursors. The relative rates of oxidative dehydrogenation of methanol and isobutanol and of hydrogenation of ethene and toluene on metals clusters in GIS, ANA, and SiO₂ and the similar cluster sizes inferred from chemisorption and TEM show that surfaces of metal clusters are clean and reside

predominantly with GIS and ANA, where they are accessible only to the smaller reactants. These conclusions were further confirmed by the ability of these materials to catalyze ethene hydrogenation in the presence of thiophene poisons. Thus, metal clusters encapsulated within ANA and GIS provide effective catalysts for the selective hydrogenation–dehydrogenation of reactants smaller than zeolite apertures over larger ones while protecting the active surfaces from large organosulfur poisons, which irreversibly bind the active surfaces. H₂-D₂ exchange rates in the presence of H₂S were much higher on M/SOD than on M/SiO₂, consistent with preferential encapsulation of metal clusters within voids protected from H₂S, making these materials potentially useful to extract H₂ via dissociative adsorption from sulfur-contaminated streams.

EXPERIMENTAL SECTION

Materials. Fumed SiO₂ (0.014 μm, 200 ± 25 m² g⁻¹, Sigma), NaAlO₂ (anhydrous, Riedel-de Haën, technical), NaOH (99.995%, Aldrich), [Pd(NH₂CH₂CH₂NH₂)₂]Cl₂ (99.9%, Aldrich), [Pd(NH₃)₄](NO₃)₂ (10 wt % in water, Aldrich), [Pt(NH₃)₄](NO₃)₂ (99.99%, Alfa Aesar), [Rh(NH₃)₅Cl]Cl₂ (Rh 34.5% min, Alfa Aesar), [Rh(NH₂CH₂CH₂NH₂)₃]Cl₃·3H₂O (≥99.5%, Aldrich), [Ru(NH₃)₆]Cl₃ (98%, Aldrich), methanol (CH₃OH, 99.9%, Aldrich), isobutanol (i-C₄H₉OH, 99.9%, Aldrich), toluene (≥99.9%, Aldrich), He (99.999%, Praxair), H₂ (99.999%, Praxair), D₂ (99.999%, Praxair), H₂-D₂ mixture (50.05% H₂, 49.95% D₂, Praxair, certified mixture), H₂S (0.5% H₂S/H₂, Praxair, certified mixture), ethene (5% C₂H₄/He, Praxair, CS), and thiophene (99%, Aldrich) were used as received.

Synthesis. Gels with molar composition of 2.0Na₂O:1.0Al₂O₃:1.5SiO₂:1.60H₂O for SOD and 5.5Na₂O:1.0Al₂O₃:4.0SiO₂:1.90H₂O for GIS were prepared. NaAlO₂ and NaOH were dissolved in demineralized H₂O and mixed with fumed SiO₂. Metal precursors [Pt(NH₃)₄](NO₃)₂, [Rh(NH₂CH₂CH₂NH₂)₃]Cl₃·3H₂O, or [Ru(NH₃)₆]Cl₃ were dissolved in 10 cm³ H₂O and added dropwise to the gel at 0.0833 cm³ s⁻¹. The gel was transferred into a 125 cm³ polypropylene container (Nalgene), sealed, and homogenized by vigorous magnetic stirring for 600 s. These gels were stirred in an oil bath at 400 rpm and 373 K for 7 h for SOD and 363 K for 3 d for GIS. The solids were collected on a fritted funnel (Pyrex 36060, 10–15 μm) and washed with deionized water until the rinse liquid reached pH 7–8. The sample was treated in ambient air at 373 K overnight, then heated in air (1.667 cm³ g⁻¹ s⁻¹) at 623 K (0.0333 K s⁻¹) for 3 h, and treated in 9% H₂/He (1.667 cm³ g⁻¹ s⁻¹, Praxair) at 573 K (0.0333 K s⁻¹) for 2 h. Samples were passivated under 0.5% O₂/He (1.667 cm³ g⁻¹ s⁻¹, Praxair) for 1 h at ambient temperature before air exposure.

The successful encapsulation of Pd clusters into SOD and GIS required initially dispersed ligand stabilized metal precursors over the SiO₂ surface. [Pd(NH₂CH₂CH₂NH₂)₂]Cl₂ was first dissolved in deionized water, and then fumed SiO₂ was added to the mixture. The resulting mixture was stirred at 400 rpm and 333 K for 3 h. Next, a solution of NaOH and NaAlO₂ was added and stirred at 400 rpm and

333 K for 1 h. The slurry temperature was raised to the crystallization temperature of the respective zeolite, and the slurry was stirred at 400 rpm. Subsequent steps were the same as for the encapsulation of Pt, Ru, and Rh in SOD and GIS.

The procedures described above were unsuccessful in the synthesis of M/ANA zeolite because the high temperatures required for ANA synthesis decomposed the metal precursors to colloidal hydroxides. Instead, M/ANA samples were prepared by adding NaOH (9 mL $\text{g}(\text{M}/\text{GIS})^{-1}$) to a previously prepared M/GIS sample, and the mixture was placed within a sealed polypropylene container. The mixture was magnetically stirred at 400 rpm for 1 h, transferred to and recrystallized in a Teflon-lined stainless steel autoclave under static conditions at 413 K for 3 d. The resulting solids were washed, dried, and treated using the procedures reported above for M/GIS samples.

The metal clusters supported on SiO_2 (Davisil, grade 646, $300 \text{ m}^2 \text{ g}^{-1}$) were prepared by the incipient wetness impregnation method using aqueous solutions of the metal precursors shown in Table 1. Silica-supported samples were dried and treated using the same procedures as zeolite-supported samples.

Physical Characterization. The identity and phase purity of zeolites and the absence of large metal structures were demonstrated by X-ray diffraction (Cu $K\alpha$ radiation $\lambda = 0.15418 \text{ nm}$, Siemens, D500). Fractional metal dispersions were determined by hydrogen chemisorption using an Autosorb-1 titration apparatus (Quantachrome). Samples were heated to 623 K at 0.0333 K s^{-1} in flowing H_2 (Praxair, 99.999%, $0.2 \text{ cm}^3 \text{ s}^{-1} \text{ g}^{-1}$) and held for 1 h and then evacuated for 1 h at 623 K to remove any chemisorbed hydrogen. Dispersions were determined from difference of total and irreversible H_2 uptakes using a 1:1 H_2 : $\text{M}_{\text{surface}}$ adsorption stoichiometry.²¹ Hydrogen adsorption isotherms were measured at 313 K and 5–50 kPa of H_2 for Pt, Ru, and Rh samples and at 343 K and 0.4–1.5 kPa of H_2 for Pd samples to prevent formation of bulk β -hydrides in Pd samples.²² Transmission electron microscopy (TEM) images were taken with a Philips 420 TEM operated at 120 kV. Before TEM investigation, the samples were embedded into an adhesive polymer, mechanically thinned, and dimpled and further thinned by Ar ion-milling (Gatan PIP Precision Ion Polishing System, 3.0 kV). High-angle annular dark-field scanning electron microscopy (HAADF STEM) images were taken with JEOL 2100 AC (aberration-corrected). Before imaging, samples were embedded and microtomed using a diamond knife to approximate thickness of 70 nm. Particle size distributions were determined by counting at least 200 crystallites in the micrographs of each sample. The surface area weighted cluster diameters, d_{TEM} , were calculated using $d_{\text{TEM}} = \sum n_i d_i^3 / \sum n_i d_i^2$ ²³ and compared to average particle diameter calculated from hydrogen chemisorption measurements to confirm the accessibility of the surface of all clusters and complete removal of ligands.

Catalytic Rate Measurements. Oxidative dehydrogenation (ODH) of alkanols, ethene and toluene hydrogenation, and H_2 – D_2 exchange rates were measured on catalyst samples diluted with fumed SiO_2 (Cab-O-Sil, HS-5, $310 \text{ m}^2 \text{ g}^{-1}$) using a quartz reactor with plug-flow dynamics. Dilution was achieved by intimate mixing at a diluent/catalyst mass ratio of 10 and pelleting and sieving the granules to retain aggregates of 0.18–0.25 mm diameter, 5–25 mg sample of which was then mixed with acid-washed quartz granules of similar size (Fluka, acid-purified, 1.0 g) to avoid intrapellet and bed gradients in concentration or temperature. Prereduced and passivated samples were treated in flowing H_2 ($1.667 \text{ cm}^3 \text{ g}^{-1} \text{ s}^{-1}$) by heating to 573 K at 0.0333 K s^{-1} and holding for 1 h before measuring hydrogenation and H_2 – D_2 exchange rates and in 20% O_2 /He flow at 393 K for 1 h before oxidation rate measurements. Alkanol oxidation rates were measured with 4 kPa of alkanol, 9 kPa of O_2 , and 87 kPa of He as diluent at 393 K, toluene hydrogenation at 0.35 kPa of toluene, 99.65 kPa of H_2 at 473 K, and ethene hydrogenation at 0.95 kPa of ethene, 5 kPa of H_2 , 94 kPa of He as diluent, and 0/0.4 kPa of thiophene at 308/315 K. H_2 – D_2 exchange rates were measured using an equimolar H_2 – D_2 mixture (50.05 kPa H_2 , 49.95 kPa D_2) and 0/1.0 kPa of H_2S at 373 K. Rates are reported as turnover rates, defined as the number of molecules converted per time normalized by the number of surface metal atoms determined from chemisorption measurements. Reactant

and product concentrations in oxidation and hydrogenation reactions were measured by gas chromatography (Agilent 6890GC) using a methyl–silicone capillary column (HP-1; $50 \text{ m} \times 0.25 \text{ mm}$, $0.25 \mu\text{m}$ film thickness) and a Porapak Q packed column (80–100 mesh, $1.82 \text{ m} \times 3.18 \text{ mm}$) connected to flame ionization and thermal conductivity detectors, respectively. H_2 – D_2 exchange rates were measured by using online mass spectrometry (Leybold Inficon, Transpector Series). Quartz, fumed SiO_2 , or metal-free zeolites did not give detectable ODH, hydrogenation, or H_2 – D_2 exchange rates, and rates on M/zeolites did not depend on extent of dilution or change with reaction time.

■ ASSOCIATED CONTENT

📄 Supporting Information

TEM image showing bulk platinum precipitation in direct hydrothermal synthesis of ANA and stability of metal precursors in alkaline solution. This material is available free of charge via the Internet at <http://pubs.acs.org>.

■ AUTHOR INFORMATION

Corresponding Author

iglesia@berkeley.edu

Present Addresses

[†]China University of Petroleum, Beijing 102249, China.

[‡]Chevron Energy Technology Company, Richmond, California 94804, United States.

Notes

The authors declare the following competing financial interest(s): (1) The funding for the research came from Chevron Energy and Technology Co. (2) Stacey I. Zones is an employee of this company and then more generally also a stockholder from Chevron Corp.

■ ACKNOWLEDGMENTS

We thank Dr. Alex Kuperman for technical input and advice, Dr. George D. Meritnez for the technical review of the manuscript, Thomas Rea for HAADF imaging, and Chevron Energy Technology for the financial support of this research.

■ REFERENCES

- (1) Gallezot, P. *Post-Synthesis Modification I* **2002**, 257.
- (2) Sachtler, W. M. H. *Acc. Chem. Res.* **1993**, 26, 383.
- (3) Gucci, L.; Kiricsi, I. *Appl. Catal., A* **1999**, 186, 375.
- (4) Zhan, B.-Z.; Iglesia, E. *Angew. Chem., Int. Ed.* **2007**, 46, 3697.
- (5) Zhan, B.-Z.; White, M. A.; Sham, T. K.; Pincock, J. A.; Doucet, R. J.; Rao, K. V. R.; Rao, Robertson, K. N.; Cameron, T. S. *J. Am. Chem. Soc.* **2003**, 125, 2195.
- (6) Csicsery, S. M. *Zeolites* **1984**, 4, 202.
- (7) Weisz, P. B.; Frillette, V. J.; Maatman, R. W.; Mower, E. B. *J. Catal.* **1962**, 1, 307.
- (8) Creighton, E.; Downing, R. *J. Mol. Catal. A: Chem.* **1998**, 134, 47.
- (9) Altwasser, S.; Gläser, R.; Weitkamp, J. *Microporous Mesoporous Mater.* **2007**, 104, 281.
- (10) Yang, H.; Chen, H.; Chen, J.; Omotoso, O.; Ring, Z. *J. Catal.* **2006**, 243, 36.
- (11) Balkus, K. J.; Gabrielov, A. G. *J. Inclusion Phenom. Mol. Recognit. Chem.* **1995**, 21, 159.
- (12) Choi, M.; Wu, Z.; Iglesia, E. *J. Am. Chem. Soc.* **2010**, 132, 9129.
- (13) Wu, Z.; Choi, M.; Iglesia, E., unpublished results.
- (14) Cundy, C. S.; Cox, P. A. *Microporous Mesoporous Mater.* **2005**, 82, 1.
- (15) Barrer, R. M. *Zeolite Synthesis*; American Chemical Society: Washington, DC, 1989; Vol. 398, p 11.
- (16) International Zeolite Association. *Atlas of Zeolite Framework Types*; <http://iza-online.org>.

- (17) Zones, S. I. *J. Chem. Soc., Faraday Trans.* **1991**, *87*, 3709.
- (18) Kohoutkova, M.; Klouzkova, A.; Maixner, J.; Mrazova, M. *Ceram.-Silik.* **2007**, *51*, 9.
- (19) Liu, H.; Iglesia, E. *J. Phys. Chem. B* **2005**, *109*, 2155.
- (20) Weitkamp, J.; Fritz, M.; Ernst, S. *Int. J. Hydrogen Energy* **1995**, *20*, 967.
- (21) Bergeret, G.; Gallezot, P. *Handbook of Heterogeneous Catalysis*; Wiley-VCH Verlag GmbH & Co. KgaA: New York, 2008.
- (22) Aben, P. J. *Catal.* **1968**, *10*, 224.
- (23) Schneider, M.; Duff, D.; Mallat, T.; Wildberger, M.; Baiker, A. J. *Catal.* **1994**, *147*, 500.